



**Ινστιτούτο Θεωρητικής και Φυσικής Χημείας
Εθνικό Ίδρυμα Ερευνών
Βασ. Κωνσταντίνου 48, Αθήνα**

ΔΙΑΛΕΞΗ

**“Preferential bonding, clustering, and phase-separation
in borosilicate and Mn-borate glasses –
a multi spectroscopic approach”**

Dr. D. Möncke

**Otto Schott Institute of Materials Research,
Friedrich Schiller University Jena, Germany**

Πέμπτη 6 Οκτωβρίου 2016, ώρα 12:00

Αίθουσα σεμιναρίων στο ισόγειο του ΕΙΕ

Preferential bonding, clustering, and phase-separation in borosilicate and Mn-borate glasses – a multi spectroscopic approach

D. Möncke^{1,2}

¹*Otto Schott Institute of Materials Research, Friedrich Schiller University Jena, Germany*

²*Theoretical and Physical Chemistry Institute, NHRF, Athens, Greece*

In low alkali borosilicate glasses, preferential bonding but also visible phase separation with physical interfaces are known to occur. Therefore, not only the question of the fraction of four- and three-fold coordinated boron deserves special consideration, but also the connectivity of the tetrahedral and trigonal borate groups with each other and with the silicate network. Older structural studies and models of borate and borosilicate glasses often invoke rules, which will be critically reconsidered.

While the addition of small amounts (~1mol%) of Al₂O₃ can prevent phase separation in low alkaline borosilicate glasses, vibrational and 2D NMR spectroscopy show a preference for B-O-B and Si-O-Si bonds over mixed B-O-Si bonds when the samples are properly annealed. More interestingly, while rapidly quenched samples show both B₄-O-Si and B₃-O-Si bonds (with B₄ and B₃ denoting four- and three-fold coordinated boron, respectively), the number of mixed bonds decreases significantly in annealed samples and, of the remaining mixed bonds, B₃-O-Si links are strongly favoured over B₄-O-Si bonds.

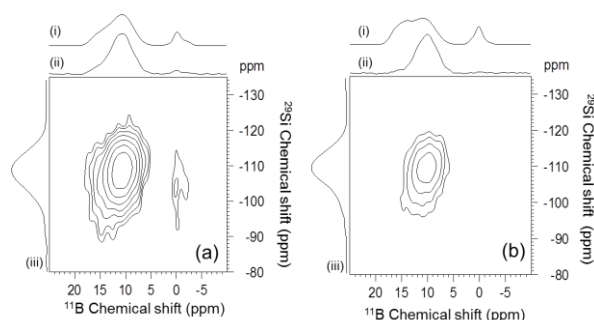


Figure 1. 2D ¹¹B/²⁹Si correlation maps of (a) quenched, (b) annealed NBS2; horizontal axis: 1D ¹¹B spectra, ¹¹B 2D map projection (ii); vertical axis: ²⁹Si 2D map projection (iii).

Addition of small amount of MnO to a duran glass, converts neutral B \emptyset ₃ into charged metaborate [B \emptyset]₄⁻ tetrahedra that bond preferentially to borate rather than to silicate entities. Clustering of Mn²⁺ ions near [B \emptyset]₄⁻ tetrahedra induce a transition from preferential bonding to finally visible phase separation. The increased clustering of Mn²⁺ ions can be followed by electron spin resonance and photo-luminescence spectroscopy. In order to follow MnO-clustering at higher concentrations the (1-2x)MnO-x(SrO-B₂O₃) system was studied. Here, borate rings consisting of three tetrahedral orthoborate units, [B \emptyset ₂O₂]³⁻, were identified by vibrational spectroscopy. These rings strengthen the glass network and a second boron oxide anomaly is observed by an increase in the glass transition temperature at very high metal oxide contents.